

INTERNATIONAL
STANDARD

ISO
25619-1

First edition
2008-12-15

**Geosynthetics — Determination of
compression behaviour**

**Part 1:
Compressive creep properties**

*Géosynthétiques — Détermination du comportement en
compression —*

Partie 1: Propriétés de fluage en compression

STANDARDSISO.COM : Click to view the full PDF of ISO 25619-1:2008



Reference number
ISO 25619-1:2008(E)

© ISO 2008

PDF disclaimer

This PDF file may contain embedded typefaces. In accordance with Adobe's licensing policy, this file may be printed or viewed but shall not be edited unless the typefaces which are embedded are licensed to and installed on the computer performing the editing. In downloading this file, parties accept therein the responsibility of not infringing Adobe's licensing policy. The ISO Central Secretariat accepts no liability in this area.

Adobe is a trademark of Adobe Systems Incorporated.

Details of the software products used to create this PDF file can be found in the General Info relative to the file; the PDF-creation parameters were optimized for printing. Every care has been taken to ensure that the file is suitable for use by ISO member bodies. In the unlikely event that a problem relating to it is found, please inform the Central Secretariat at the address given below.

STANDARDSISO.COM : Click to view the full PDF of ISO 25619-1:2008



COPYRIGHT PROTECTED DOCUMENT

© ISO 2008

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized in any form or by any means, electronic or mechanical, including photocopying and microfilm, without permission in writing from either ISO at the address below or ISO's member body in the country of the requester.

ISO copyright office
Case postale 56 • CH-1211 Geneva 20
Tel. + 41 22 749 01 11
Fax + 41 22 749 09 47
E-mail copyright@iso.org
Web www.iso.org

Published in Switzerland

Contents

	Page
Foreword	iv
1 Scope	1
2 Normative references	1
3 Terms and definitions	1
4 Test specimens	2
4.1 Sampling	2
4.2 Number and dimensions of test specimens	2
4.3 Conditioning	5
5 Normal compressive load method	6
5.1 Principle	6
5.2 Apparatus	6
5.3 Procedure	9
5.4 Calculations	9
5.5 Test report	10
6 Combined normal and shear load method	11
6.1 Principle	11
6.2 Apparatus	11
6.3 Procedure	14
6.4 Calculations	15
6.5 Test report	16
Annex A (informative) Variations to the index test procedure for site-specific tests	18
Annex B (informative) Typical curves	19

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

International Standards are drafted in accordance with the rules given in the ISO/IEC Directives, Part 2.

The main task of technical committees is to prepare International Standards. Draft International Standards adopted by the technical committees are circulated to the member bodies for voting. Publication as an International Standard requires approval by at least 75 % of the member bodies casting a vote.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights.

ISO 25619-1 was prepared by the European Committee for Standardization (CEN) Technical Committee CEN/TC 189, *Geosynthetics*, in collaboration with ISO Technical Committee ISO/TC 221, *Geosynthetics*, in accordance with the Agreement on technical cooperation between ISO and CEN (Vienna Agreement).

This first edition of ISO 25619-1 cancels and replaces EN 1897:2001, which has been technically revised. The following technical changes have been introduced:

- normative references have been updated;
- definitions, in particular with regard to compressive creep strain (ε_{cc}), have been clarified;
- omission of conditioning of the test specimen has been allowed under specific circumstances, and the circumstances under which immersed specimens should be tested have been specified;
- a requirement has been included that the stress applied by the top plate on the specimen shall not exceed 2 kPa;
- calculation of compressive creep strain has been included in addition to total compressive strain; a requirement has been included that it be referred to in the test report and that a plot of compressive creep strain versus log (time) be provided (for both test methods).

ISO 25619 consists of the following parts, under the general title *Geosynthetics — Determination of compression behaviour*:

- *Part 1: Compressive creep properties*
- *Part 2: Determination of short-term compression behaviour*.

Geosynthetics — Determination of compression behaviour —

Part 1: Compressive creep properties

1 Scope

This part of ISO 25619 specifies index test methods for determining the compressive creep properties of geosynthetic products. The test specimens are subjected either to normal compressive loading or to a combination of normal compressive loading and shear loading.

The test method with a normal load only (see Clause 5) is the standard method.

The test method in which both normal and shear loads are applied (see Clause 6) is intended for products that are sensitive to shear failure, i.e. which have a columnar or cusped structure.

The tests are carried out on dry specimens or on specimens immersed in water. The test is intended to be carried out with the specimen immersed in water when any part of the geosynthetic product contains a hydrophilic polymer.

2 Normative references

The following referenced documents are indispensable for the application of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 554, *Standard atmospheres for conditioning and/or testing — Specifications*

ISO 3696, *Water for analytical laboratory use — Specification and test methods*

ISO 9862, *Geosynthetics — Sampling and preparation of test specimens*

ISO 9863-1, *Geosynthetics — Determination of thickness at specified pressures — Part 1: Single layers*

ISO 10318, *Geosynthetics — Terms and definitions*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in ISO 10318 and the following apply.

3.1

thickness

d

distance between the two rigid plates in contact with the specimen at any stage of the test

See Figures 1 and 2.

NOTE Thickness is measured in millimetres.

3.2

initial thickness

d_i

thickness of the specimen under an applied normal stress of 2 kPa

NOTE Initial thickness is measured in millimetres, in accordance with ISO 9863-1.

3.3

initial compressed thickness

d_0

thickness measured 1 min after loading (normal loading) or 4 min after loading (normal and shear loading)

3.4

total compressive strain

ε

time-dependent change in thickness

NOTE Total compressive strain is expressed as a percentage of the initial thickness (d_i).

3.5

compressive creep strain

ε_{cc}

time-dependant change in thickness of a material subjected to a constant compressive load (after reaching the initial compressed thickness, d_0 , of the specimen)

NOTE Compressive creep strain is expressed as a percentage of the initial compressed thickness.

3.6

compressive creep collapse

occurrence of a sudden increase in the speed of change of thickness of a specimen subjected to a constant compressive load

4 Test specimens

4.1 Sampling


Specimens shall be taken in accordance with ISO 9862.

4.2 Number and dimensions of test specimens

Cut two specimens from the test sample for each test load; a new specimen is required for each test.

Each specimen shall satisfy the following criteria with regard to dimensions:

- the specimen shall be square and have a minimum size of 100 mm × 100 mm (see Figures 1 and 2); if the specimen has a structure in which loading is resisted at defined points or areas, then the loading plate shall cover at least three complete points or areas in both directions (see Figure 3);
- specimens shall be cut with the sides parallel to the length and width of the sample.

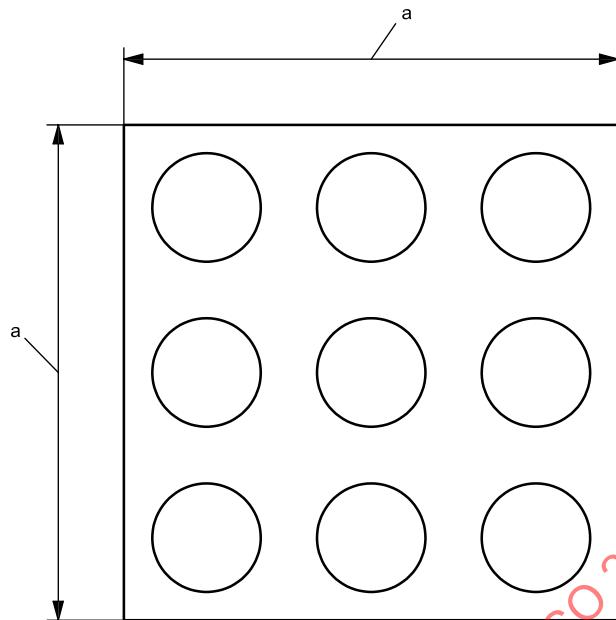

a) Plan area

a 100 mm minimum, or at least three contact points in each direction.




b) Cross-sectional area

Key


d thickness of the specimen, in millimetres

Figure 1 — Dimensions of general test specimen

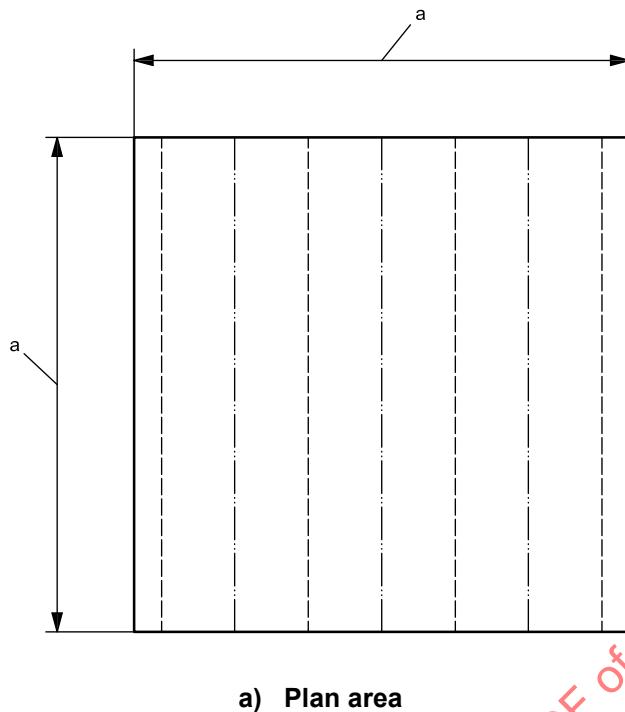

a) Plan area

- a 100 mm minimum, or a minimum of three contact lines on the top plate and a minimum of four contact lines on the base plate.

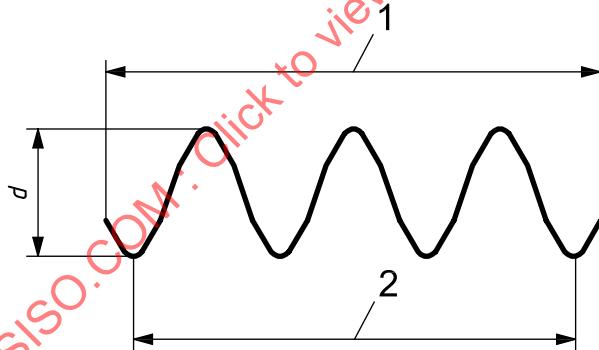


b) Cross-sectional area


Key

- 1 specimen width
- 2 representative width of the specimen
- d thickness of specimen, in millimetres

**Figure 2 — Size of specimen of a geomat
(with wave structure or double-sided structured core of a drainage composite)**

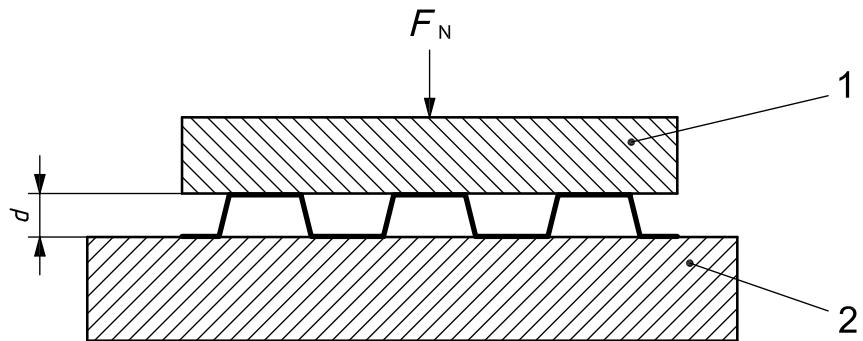

a) Example for single-sided structured cores

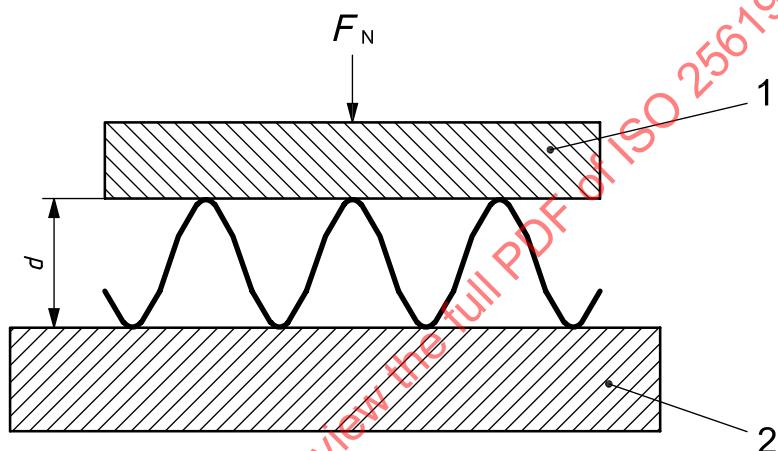

b) Example for double-sided structured cores

Key

- 1 metal top plate, smooth surface (same size as specimen or larger)
- 2 metal base plate, smooth surface (larger than top plate)
- d thickness of specimen, in millimetres
- F_N applied normal force, in kilonewtons

Figure 3 — Loading arrangements for structured cores

4.3 Conditioning

The test specimens shall be conditioned and tested in the standard atmosphere for testing at $(20 \pm 2)^\circ\text{C}$ and $(65 \pm 5)\%$ relative humidity, as defined in ISO 554.

The specimens can be considered to have been conditioned when the change in mass in successive weighings made at intervals of not less than 2 h does not exceed 0,25 % of the mass of the test specimen.

Conditioning and/or testing in the standard atmosphere may only be omitted when it can be shown that results obtained for the same specific type of product (both structure and polymer type) are not affected by changes in temperature and humidity exceeding the limits. This information shall be included in the test report.

The test shall be carried out with the specimen immersed in water when any part of the geosynthetic product contains a hydrophilic polymer. Where the test is to be carried out with the specimen immersed in water, the specimen shall be soaked in water for 24 h prior to the test. Deionized water in accordance with ISO 3696 shall be used. The water shall be maintained at a temperature of $(20 \pm 2)^\circ\text{C}$.

5 Normal compressive load method

5.1 Principle

The geosynthetic specimen is placed on the fixed base of the compression testing equipment. With an upper loading plate, the vertical compressive load is applied and the change in thickness is recorded with time.

The vertical compressive load is applied to the specimen for a period of 1 000 h, or for a longer or shorter period by agreement.


5.2 Apparatus

5.2.1 Compression testing equipment.

Compression testing equipment with a vertical travel greater than the initial thickness of the specimen shall be used. It shall be capable of sustaining the applied stress to within 1 % accuracy for the duration of the test.

The compressive stress may be applied mechanically, pneumatically or hydraulically. Where hydraulic or pneumatic loading systems are used, the stress applied shall be constant for the duration of the test. The loading device, however, shall be capable of applying the full stress in one controlled step, i.e. without significant impact, within a period of 60 s.

Most systems use dead weights to apply the stress. In systems using dead weights, the loading system shall be fully supported while being assembled so that no forces are applied to the specimen until the support is smoothly released [see Figure 4 a)].

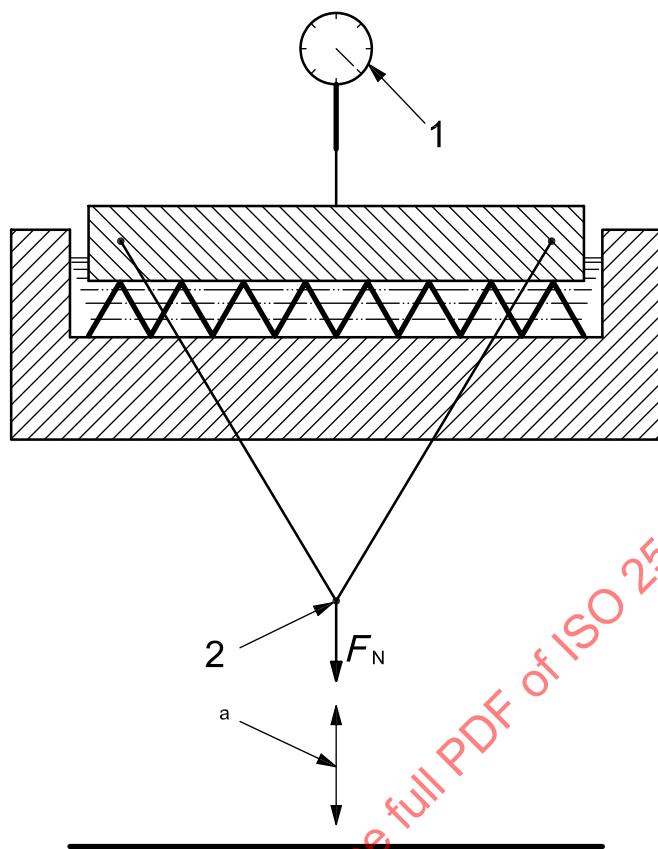


a) Normal load test

Key

- 1 measuring device
- 2 weights on hanger
- F_N applied normal force, in kilonewtons
- a Load supported prior to starting.

Figure 4 (continued)

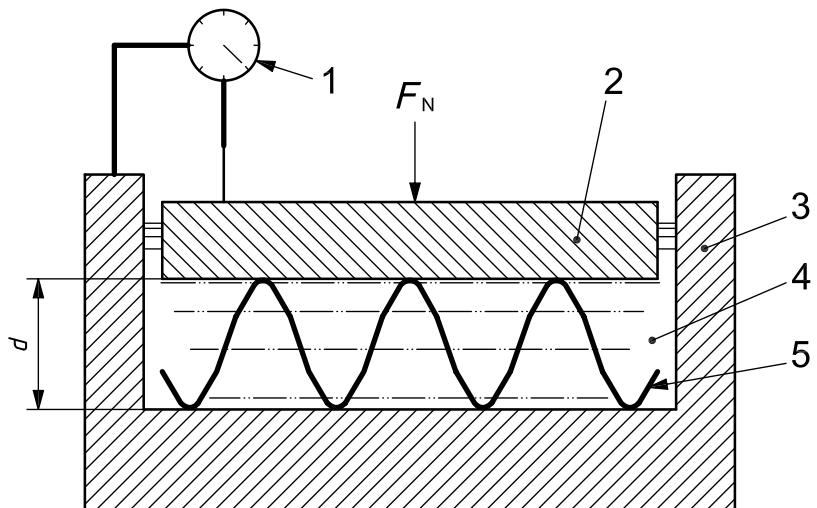

b) Normal load test under water

Key

- 1 measuring device(s), minimum of three if a single unit placed centrally is not used
- 2 metal top loading plate, smooth surface (same size as specimen or larger)
- 3 metal base plate, smooth surface (larger than top plate), with specimen container for water bath (if required)
- 4 water (if required)
- 5 specimen
- d thickness of the specimen, in millimetres
- F_N applied normal force, in kilonewtons

Figure 4 — Examples of typical arrangements for normal load tests

The compression testing apparatus shall include a fixed base plate and a parallel moveable top plate, both with a flat and smooth metal surface. The dimensions of the top plate shall be at least equal to those of the specimen and its thickness shall be such that it will result in a normal stress of not greater than 2 kPa being applied to the specimen (see Figure 3).

5.2.2 Specimen container.

If the test is carried out with the specimen immersed in water, a container to keep the specimen immersed and at a constant temperature shall be used. The water level in the container shall cover the specimen but the height of water above the specimen shall not exceed 25 mm.

5.2.3 Thickness measurement device.

A means of measuring the mean thickness of the specimen to an accuracy of 0,02 mm shall be used. Unless measurements are taken at the centre of the specimen, measurements shall be taken at a minimum of three equally spaced points. If three or more measurement points are used, the thickness is the mean of the values recorded.

5.2.4 Timer.

Time shall be recorded throughout the test period.

5.3 Procedure

Measure the initial thickness of the specimen in accordance with ISO 9863-1, using a normal stress of 2 kPa. After measuring the initial thickness, install the same specimen in the compression testing equipment.

Ensure that the specimen is placed symmetrically on the base plate and covered with the top plate.

Apply the load needed to give the required normal compressive stress in less than 60 s.

The normal stresses to be applied shall include at least four of the following: 20 kPa, 50 kPa, 100 kPa, 200 kPa and 500 kPa, to an accuracy of $\pm 2\%$.

A new specimen is to be used for each test; two specimens shall be tested at each of the specified stresses.

Record the thickness of the specimen at the following times after the application of the test stress:

- 1 min, 2 min, 4 min, 15 min, 30 min, 60 min;
- 2 h, 4 h, 8 h, 24 h;
- 2 d, 4 d, 7 d, 14 d, 28 d, 42 d.

The test may be terminated when the recorded thickness of the specimen is less than 10 % of the initial thickness.

Repeat the test on the other specimens. Carry out calculations as indicated in 5.4.

5.4 Calculations

Applied normal stress is calculated using Equation (1):

$$\sigma = F_N / A \quad (1)$$

where

σ is the applied normal stress, in kilopascals;

F_N is the applied normal force, in kilonewtons;

A is the area of specimen, in square metres.

NOTE For wave-type structures [see Figure 2 b)], the representative width is used to calculate the area of the specimen.

The area of a cuspated or columnar sample shall be calculated by counting the number of contact points in a 1,0 m width and length to determine the number of contact points in 1,0 m². The area of specimen (A) is then calculated using Equation (2):

$$A = \frac{N_s}{N_u} \quad (2)$$

where

N_s is the number of contact points in the specimen;

N_u is the number of contact points per square metre.

Compressive creep strain, in percent, is calculated using Equation (3):

$$\varepsilon_{cc} = 100 \times (d_0 - d_x)/d_0 \quad (3)$$

where

ε_{cc} is the compressive creep strain, in percent;

d_0 is the initial compressed thickness, in millimetres;

d_x is the thickness under load, in millimetres, at time x .

Total compressive strain is calculated at each time interval using Equation (4):

$$\varepsilon = 100 \times (d_i - d_x)/d_i \quad (4)$$

where

ε is the total compressive strain, in percent;

d_x is the thickness under load, in millimetres, at time x ;

d_i is the initial thickness, in millimetres, at 2 kPa.

5.5 Test report

The test report shall include the following information:

- a) dated reference to this part of ISO 25619, i.e. ISO 25619-1:2008;
- b) identification of the sample according to ISO 10318, date of receipt and date of testing;
- c) conditioning atmosphere;
- d) whether the test was carried out dry or with the specimen immersed in water;
- e) size of the specimen and the initial thickness (d_i) of the specimen at 2 kPa;
- f) the initial compressed thickness (d_0), in millimetres, under a load of x kPa;
- g) the stress levels used in the test;
- h) the mean thickness, in millimetres, the compressive creep strain (ε_{cc}), in percent, and the total compressive strain (ε), in percent, of the specimens at 1 h and 1 000 h for each of the specified pressures;
- i) any agreed deviation from the procedure;

NOTE 1 Some possible deviations are listed in Annex A.

- j) any unusual behaviour, e.g. compressive creep collapse of the core structure;
- k) for cusped or columnar geocomposite products, the number of points in contact with the loading plates; for wave structures, the number of waves in contact with the loading plates;
- l) a plot of the thickness (d) against log time (t) for each specimen and each of the normal pressures used in the test;

- m) a plot of total compressive strain (ε) against log time (t) for each specimen and each of the normal pressures used;

NOTE 2 Figure B.1 shows a typical response.

- n) a plot of compressive creep strain (ε_{cc}) against log time (t) for each of the pressures used in the test.

6 Combined normal and shear load method

6.1 Principle

The geosynthetic specimen is placed on the fixed base of the compression testing equipment with an upper loading plate and base plate both of sufficient roughness to permit the development of any required shear forces.

The vertical compressive load and horizontal shear forces are applied to the geosynthetic specimen and the change in thickness and lateral displacement are recorded with time. The vertical compressive load and the shear force are to be applied for a minimum period of 1 000 h, or for a longer or shorter period by agreement.


6.2 Apparatus

6.2.1 Compression testing equipment.

Compression testing equipment with a vertical travel greater than the nominal thickness of the specimen shall be used. It shall be capable of sustaining the applied stress to within 1 % accuracy for the duration of the test.

The compressive stress may be applied mechanically, pneumatically, or hydraulically. Where a hydraulic or pneumatic system is used, the stress applied shall be constant for the duration of the test. The loading device, however, shall be capable of applying the full magnitude of the vertical test load in one controlled step, i.e. no significant impact, within a period of 60 s.

Most systems use dead weights for the load which should be fully supported while being assembled such that no forces are applied to the specimen until the support is smoothly released [see Figure 5 b)]. The horizontal force can be applied simultaneously with the normal load or may be applied separately but commencing not less than 60 s after the application of the full normal compressive load. The horizontal force is to be applied in one controlled step, i.e. no significant impact, within a period of 3 min after application of the full pressure.

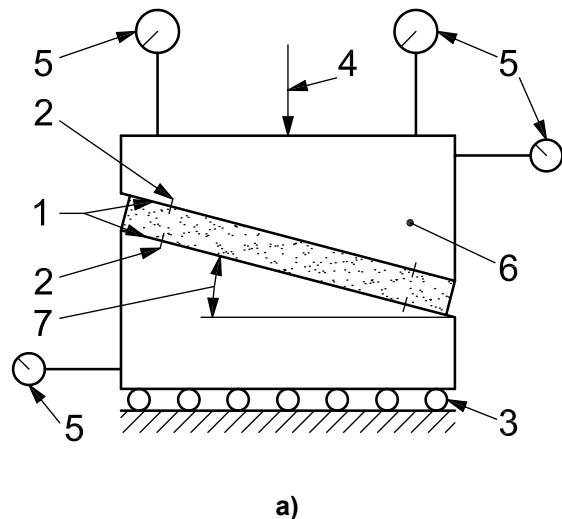


a)

Key

- 1 roughened surfaces
- 2 witness marks (to show that slip between plates and specimen does not take place)
- 3 rollers (to allow horizontal movement of bottom plate)
- 4 applied normal force
- 5 measuring devices (2 vertical, 2 horizontal)
- 6 top plate (either free to move or fixed)
- 7 slope, S (for $S = 20\%$, $\theta = 11,3^\circ$)

Figure 5 (continued)

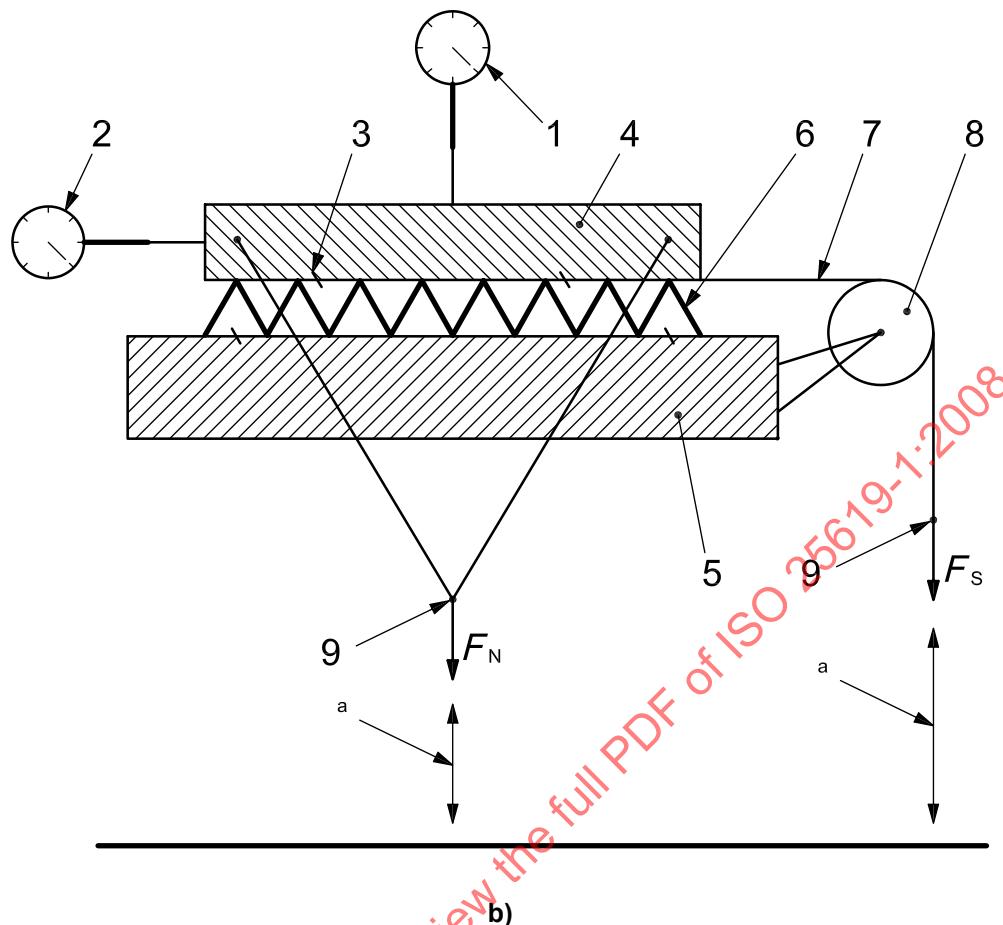**Key**

- 1 vertical measuring device (single unit placed centrally)
- 2 horizontal measuring device (single unit placed centrally)
- 3 witness marks
- 4 metal top loading plate, rough surface (same size as specimen or larger)
- 5 metal base plate, rough surface (larger than top plate)
- 6 specimen
- 7 steel rope
- 8 roll
- 9 weights on hanger
- F_N applied normal force
- F_S applied shear force
- a Load supported prior to starting.

Figure 5 — Typical loading arrangements for combined normal and shear loadings

The compression testing apparatus shall include a steel base plate and a steel top plate, one of which shall be fixed and the other with freedom of movement in both the vertical and horizontal directions. The plates shall have sufficient roughness to permit the development and transfer of the required shear forces, alternatively the normal pressure can be rotated to produce a horizontal component. The top plate shall have dimensions at least equal to those of the specimen and a thickness which will result in the application of a normal stress to the specimen of not more than 2 kPa (see Figure 3).

It is important when using dead loads to apply the horizontal shear force in such a way that the line of action of the horizontal load is in the same horizontal plane as the interface between the top plate and the specimen.

6.2.2 Specimen container.

If the specimen is to be immersed in water, a container to keep the specimen immersed and at a constant temperature shall be used. The water level in the container shall cover the specimen, but the height of water above the specimen shall not exceed 25 mm.

6.2.3 Thickness measurement device.

A means of measuring the mean thickness of the specimen to an accuracy of 0,02 mm shall be used. Unless measurements are taken at the centre of the specimen, measurements shall be taken at a minimum of at least three equally spaced points. If three measurement points are used, the thickness is the mean of the three values recorded.

6.2.4 Shear measurement device.

A means of measuring the shear displacements of the specimen to an accuracy of 0,02 mm shall be used.

6.2.5 Timer.

Time shall be recorded throughout the test period.

6.3 Procedure

Measure the initial thickness of the specimen in accordance with ISO 9863-1 using a normal stress of 2 kPa. After measuring the initial thickness (d_i) install the same specimen in the compression testing equipment.

Ensure that the specimen is placed symmetrically on the base plate and covered with the top plate.

Where independent loading for normal load and shear load are used, apply the load needed to give the required normal compressive stress in less than 60 s and the required shear stress in less than 3 min. Where the shear load is achieved by the use of angled plates, the load needed to give the required normal and shear stresses should be applied in less than 4 min.

The normal stresses to be applied shall include at least four of the following: 20 kPa, 50 kPa, 100 kPa, 200 kPa and 500 kPa, to an accuracy of $\pm 2\%$.

NOTE Some possible deviations from the method are listed in Annex A.

The shear force shall be equal to 20 % of the normal force.

A new specimen is to be used for each test; two specimens are to be tested at each of the specified stresses.

If a shear force is not only applied along the machine direction, then further specimens shall be tested with the shear force along the cross-machine direction of the specimen.

Record the thickness of the specimen and the shear displacement at the following time intervals after the application of the normal test stress:

- 4 min, 15 min, 30 min, 60 min;
- 2 h, 4 h, 8 h, 24 h;
- 2 d, 4 d, 7 d, 14 d, 28 d, 42 d.

The test may be terminated when the recorded thickness of the specimen is less than 10 % of the initial thickness.

Repeat the test on the other specimens. Carry out calculations as specified in 6.4.

6.4 Calculations

Applied normal stress is calculated using Equation (5):

$$\sigma = F_N/A \quad (5)$$

where

σ is the applied normal stress, in kilopascals;

F_N is the applied force, in kilonewtons;

A is the area of specimen, in square metres.

NOTE For wave-type structures [see Figure 2 b)], the representative width is used to calculate the area of the specimen.

The area of a cusped or columnar sample shall be calculated by counting the number of contact points in a 1,0 m width and length to determine the number of contact points in 1,0 m². The area of specimen (A) is then calculated using Equation (6):

$$A = \frac{N_s}{N_u} \quad (6)$$

where

N_s is the number of contact points in the specimen;

N_u is the number of contact points per square metre.

Compressive creep strain is calculated using Equation (7):

$$\varepsilon_{cc} = 100 \times (d_0 - d_x)/d_0 \quad (7)$$

where

ε_{cc} is the compressive creep strain, in percent;

d_0 is the initial compressed thickness, in millimetres;

d_x is the thickness under load, in millimetres, at time x .

Total compressive strain is calculated at each time interval using Equation (8):

$$\varepsilon = 100 \times (d_i - d_x)/d_i \quad (8)$$

where

ε is the total compressive strain, in percent;

d_x is the thickness, in millimetres, at time x ;

d_i is the initial thickness of the specimen, in millimetres, at 2 kPa.

Calculate the shear stress applied to the specimen using Equation (9):

$$\tau = F_s / A \quad (9)$$

where

- τ is the shear stress, in kilopascals;
- F_s is the applied shear force, in kilonewtons;
- A is the area of the specimen, in square metres.

Calculate the shear strain using Equation (10):

$$\gamma = 100 \times (\Delta s / d_i) \quad (10)$$

where:

- γ is the shear strain, in percent;
- Δs is the displacement of one face relative to the other, in millimetres;
- d_i is the initial thickness of the specimen, in millimetres.

6.5 Test report

The test report shall include the following information:

- a) dated reference to this part of ISO 25619, i.e. ISO 25619-1:2008;
- b) identification of the sample according to ISO 10318, date of receipt and date of testing;
- c) conditioning atmosphere;
- d) whether the test was carried out dry or with the specimen immersed in water;
- e) size of specimen and the initial thickness (d_i) of the specimen at 2 kPa;
- f) the initial compressed thickness (d_0), in millimetres, under a load of x kPa;
- g) the stresses (σ) and the shear loads (τ) used in the test;
- h) the mean thickness, in millimetres, the compressive creep strain (ε_{cc}), in percent, and the total compressive strain (ε), in percent, of the specimens at 1 h and 1000 h for each of the specified pressures and shear loads (and, if appropriate, in both directions);
- i) any agreed deviation from the procedure;

NOTE 1 Some possible deviations are listed in Annex A.

- j) any unusual behaviour, e.g. compressive creep collapse of the core or shear failure of the interface between the filter and the core of the drainage geocomposite;
- k) for cusped or columnar geocomposite products, the number of points in contact with the loading plates; for wave structures, the number of waves in contact with the loading plates;
- l) a plot of the thickness (d) against log time (t) for each specimen at each of the normal and shear loads used in the test;